

**OPEN ACCESS**

## A STEM study of twin defects in $\text{Fe}_3\text{O}_4(111)/\text{YZO}(111)$

To cite this article: D Gilks *et al* 2014 *J. Phys.: Conf. Ser.* **522** 012036

View the [article online](#) for updates and enhancements.

### Related content

- [Origin of anomalous magnetite properties in crystallographic matched heterostructures:  \$\text{Fe}\_3\text{O}\_4\(111\)/\text{MgAl}\_2\text{O}\_4\(111\)\$](#)   
D Gilks, L Lari, J Naughton *et al.*
- [Structural investigation of precipitates with Cu and Zn atomic columns in Al-Mg-Si alloys by aberration-corrected HAADF-STEM](#)  
Takeshi Saito, Calin D Marioara, Sigmund J Andersen *et al.*
- [Characterisation of Nanoparticle Structure by High Resolution Electron Microscopy](#)  
Robert D Boyd, Rickard Gunnarsson, Iris Pilch *et al.*



**IOP | ebooks™**

Bringing you innovative digital publishing with leading voices to create your essential collection of books in STEM research.

Start exploring the collection - download the first chapter of every title for free.

## A STEM study of twin defects in Fe<sub>3</sub>O<sub>4</sub>(111)/YZO(111)

D Gilks<sup>1</sup>, L Lari<sup>1,2</sup>, K Matsuzaki<sup>3</sup>, R Evans<sup>1</sup>, K McKenna<sup>1</sup>, T Susaki<sup>3</sup>, V K Lazarov<sup>1</sup>.

<sup>1</sup>Department of Physics, University of York, Heslington, York, YO10 5DD, UK

<sup>2</sup>York-JEOL Nanocentre, University of York, Heslington, York, YO10 5BR, UK


<sup>3</sup>Secure Materials Centre, Materials and Structures Laboratory, Tokyo Institute of Technology, 4259 Nagatsuta, Midori-ku, Yokohama 226-8503, Japan

E-mail: dg522@york.ac.uk

**Abstract.** We observe twin defects on both the (111) and (11-2) planes of thin film Fe<sub>3</sub>O<sub>4</sub> using atomically resolved high angle annular dark field (HAADF) STEM imaging. These defects are significant for understanding the previously reported anomalous properties of Fe<sub>3</sub>O<sub>4</sub> films as they generate non-bulk bonding configurations leading to non-bulk superexchange interactions in these regions.

### 1. Introduction

Bulk Fe<sub>3</sub>O<sub>4</sub> (Figure 1) is a predicted half metal with a 100% spin polarisation at the Fermi level. [1, 2]. This bulk property makes thin film Fe<sub>3</sub>O<sub>4</sub> of interest for future spintronics device applications [3-6]. However, structural defects including anti-phase boundaries (APB) in thin film Fe<sub>3</sub>O<sub>4</sub> prevent the fabrication of films with bulk Fe<sub>3</sub>O<sub>4</sub> properties. Thin film Fe<sub>3</sub>O<sub>4</sub> exhibits negative magnetoresistance and does not magnetically saturate, e.g. bulk Fe<sub>3</sub>O<sub>4</sub> shows no magneto-resistance and magnetically saturates at low applied fields. This makes a thorough understanding of defect formation in thin film

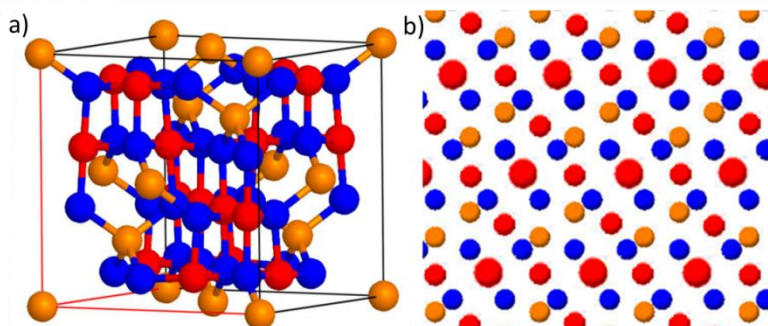

**Figure 1.** a) The unit cell of Fe<sub>3</sub>O<sub>4</sub> consisting of 32 O atoms, 16 Fe in octahedral (B) positions and 8 Fe in tetrahedral positions (A). b) Fe<sub>3</sub>O<sub>4</sub> viewed along the [1-10] direction showing all the atomic columns occupied by single atom types.

Fe<sub>3</sub>O<sub>4</sub> essential. The presence of APB defects is well documented in the literature [7-9]. In this paper we show that twin defects are also present in epitaxially grown single crystal films and their presence should be taken into account to fully understand the functional properties of Fe<sub>3</sub>O<sub>4</sub> thin films. We observe twin defects in Fe<sub>3</sub>O<sub>4</sub> films grown on Yttrium stabilized Zirconium Oxide (YZO). Currently twin defects in thin film Fe<sub>3</sub>O<sub>4</sub> have



not received significant research attention, consequently the impact of twin defects on the overall magnetic and transport properties of thin film  $\text{Fe}_3\text{O}_4$  are not well known at present.


## 2. Methods

High angle annular dark field scanning transmission electron microscopy (HAADF-STEM) data has been collected using a JEOL 2200FS microscope operating at 200kV and equipped with CEOS 3<sup>rd</sup> order imaging and probe aberration correctors. Diffraction patterns have been acquired using a JEOL 2011. Image simulations have been calculated using parallelised QSTEM image simulation software [10] with 30 thermal diffuse scattering iterations performed for each simulation. Aberration coefficients values used for the simulations were  $C_s$  (1.1  $\mu\text{m}$ ),  $C_5$  (1.76 mm) and  $C_c$  (1.6 mm) respectively, as measured by the CEOS corrector software before HAADF image acquisition.  $\text{Fe}_3\text{O}_4$  films have been grown using PLD methods with a KrF excimer laser incident on a  $\text{Fe}_3\text{O}_4$  target, films were grown at 300 °C in an oxygen partial pressure of  $2 \times 10^{-4}$  Pa followed by high temperature post-annealing at 1100 °C in a CO/CO<sub>2</sub> atmosphere as discussed elsewhere [11]. TEM samples have been produced by mechanical thinning and low angle argon ion milling to electron transparency following the protocol described in [12].

## 3. Results and Discussion


The annealed films show atomically sharp film/substrate interfaces and uniform film thickness across the samples as shown in Figure 2. We find two types of twin defects in these films. The first type of twin defect propagates in the film growth direction from the film/substrate interface to the film surface (Figure 3). These defects are not seen to nucleate or discontinue within the film, nor are they seen to deviate from the single (11-2) planes on which they are located. The second type of twin defect is perpendicular to the growth direction on a (111) twin-plane, Figure 4; as the first type of defects they are also atomically sharp.

In the (11-2) twins, we observe defects originating from bunched step edges in the YZO substrates indicating that surface steps could be potential twin nucleation sites. We have also observed that the twins are highly mobile whilst being annealed at 1100 °C, as their density drops considerably as a result of the annealing process. From this it is unclear whether the twin defects nucleate as a result of the substrate step edges, or migration of twin defects during the annealing procedure pins them to the step edges. By studying a series of films with varied annealing times (or temperatures) and the resultant defect density and morphology it should be possible to identify a relationship between initial deposition characteristics in the films and the evolution of these defects during the annealing procedure.

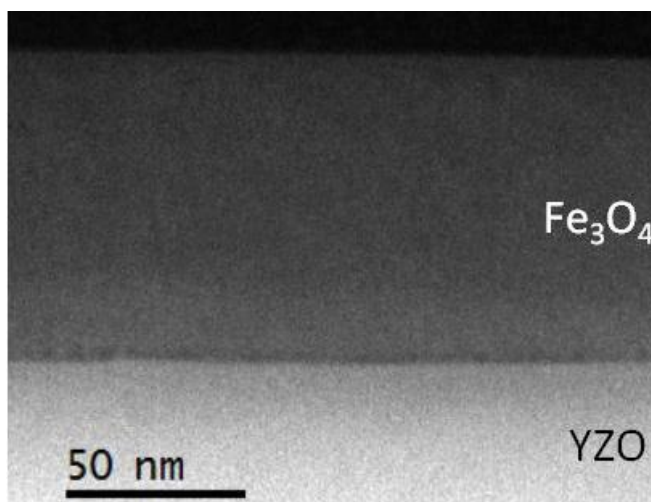


**Figure 2.** HAADF-STEM image of a  $\text{Fe}_3\text{O}_4$  film grown on YZO substrate.

Several scenarios are possible to create twin defects in  $\text{Fe}_3\text{O}_4$  grown on YZO. The underlying stacking sequence of the YZO substrate should 'direct' the stacking of the  $\text{Fe}_3\text{O}_4$  film and give a preferred stacking sequence in the deposited film, however, in these films it seems that the stacking sequence through the interface is often not maintained. This suggests that stacking faults at the  $\text{Fe}_3\text{O}_4$ /YZO interface are either of low formation energy or different surface termination of YZO can provide growth templates for different atomic films-substrate interfaces which ultimately result in twin-related stacking sequence that propagate as the films is grown.

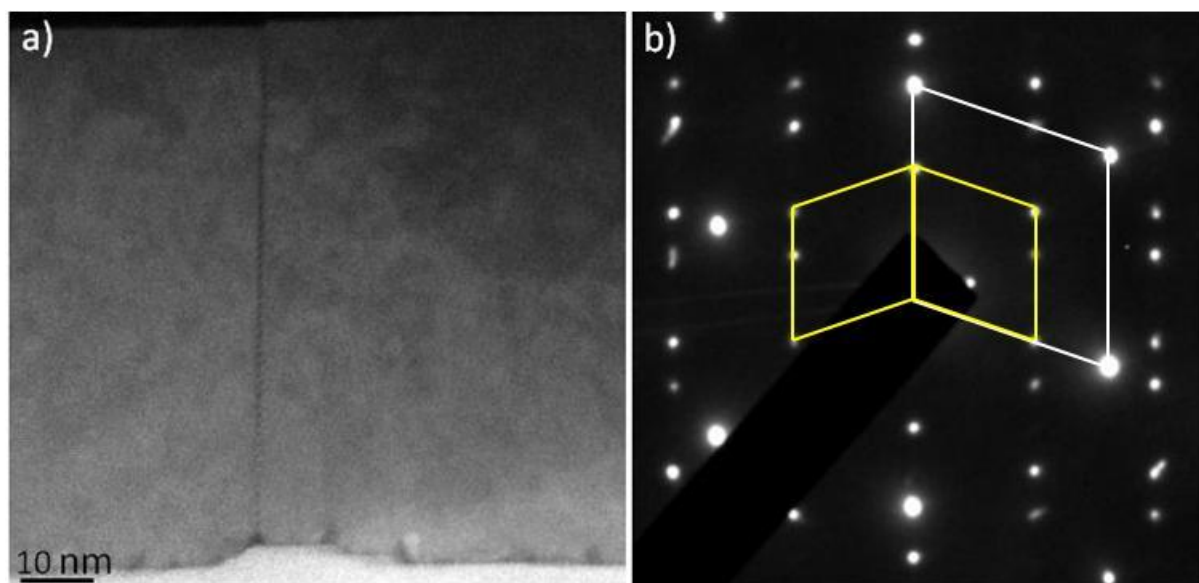

**Figure 3.** HAADF-STEM and diffraction patterns of a twin defect in  $\text{Fe}_3\text{O}_4$  imaged in the  $[1-10]$  zone axis. a) Shows a twin running vertically from a stepped region of the film/substrate interface to the film surface. b) Shows the overlaid diffraction patterns of the YZO substrate (white/largest rhombus) and two  $\text{Fe}_3\text{O}_4$  diffraction patterns (two yellow/smaller rhombuses) the twinned structure can be identified through the mirror symmetry of the  $\text{Fe}_3\text{O}_4$  diffraction spots from left to right in the pattern.

The twin structures we observe running perpendicular to the growth direction demonstrate that  $\text{Fe}_3\text{O}_4$  can form twins even when the underlying stacking sequence of well ordered  $\text{Fe}_3\text{O}_4$  is already present in the film. This indicates the formation energy of twins defects on the  $(111)$  plane of  $\text{Fe}_3\text{O}_4$  is low. In the twin defects we have observed the octahedrally co-ordinated  $\text{Fe}_B$  plane appears to form the twin with structural symmetry about this plane.

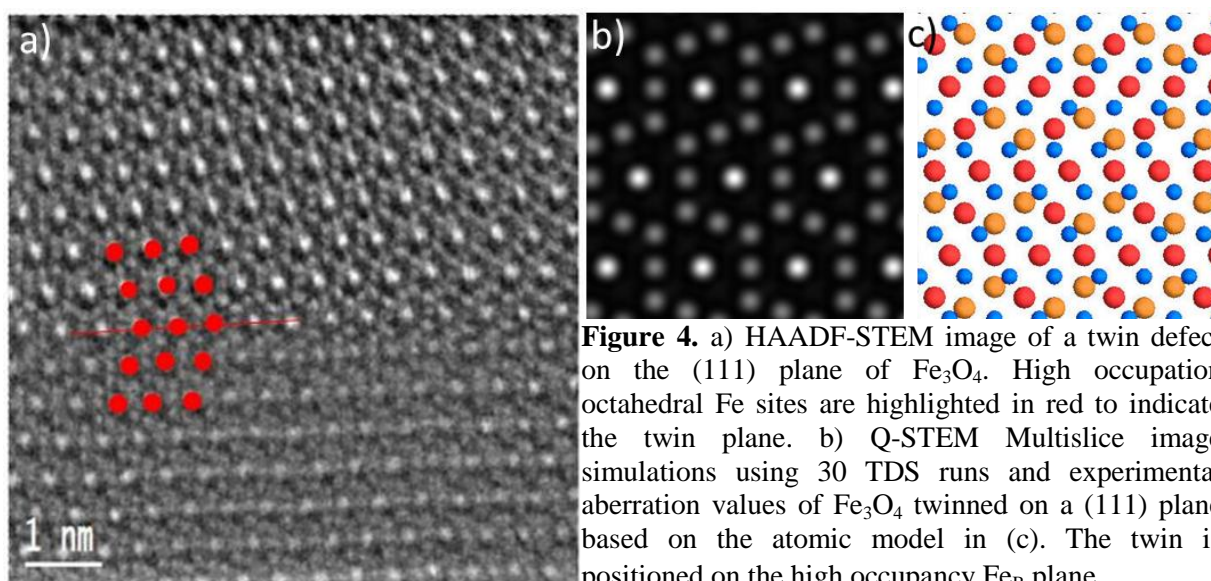

**Figure 4.** a) HAADF-STEM image of a twin defect on the  $(111)$  plane of  $\text{Fe}_3\text{O}_4$ . High occupation octahedral Fe sites are highlighted in red to indicate the twin plane. b) Q-STEM Multislice image simulations using 30 TDS runs and experimental aberration values of  $\text{Fe}_3\text{O}_4$  twinned on a  $(111)$  plane based on the atomic model in (c). The twin is positioned on the high occupancy  $\text{Fe}_B$  plane.

Unlike in the (11-2) plane defect, this (111) twin does not lead to a heavily relaxed interfacial structure, rather the Fe<sub>3</sub>O<sub>4</sub> structure simply continues but with an inversion of the stacking sequence across the twin boundary. From the Figure 4 it can be observed that the octahedral Fe-O-Fe bond angles are significantly increased compared to 90° bonds in bulk Fe<sub>3</sub>O<sub>4</sub>. This is of importance as the bond angles define the superexchange interactions between Fe-O-Fe sites. As bond angles between Fe sites increase the superexchange interaction become strongly anti-ferromagnetic.

#### 4. Conclusions

We show direct evidence of two distinct styles of twin boundaries in thin film Fe<sub>3</sub>O<sub>4</sub>. While the origin of the vertical (11-2) twin defects could be influenced by several mechanisms, the formation of perpendicular (111) twins is most likely driving by their low formation energy. The effect of twin structural defects on the magnetic and magneto-transport properties of magnetite thin films is still to be explored. These properties will be studied using atomistic magnetic modelling and *ab. Initio* structural refinement and electronic structure calculations. This will allow a comparison between simulated magnetisation properties and structure with experimental in-plane magnetisation and transport measurements.

- [1] Yanase A and Siratori K 1984 Band-Structure in the High-Temperature Phase of Fe<sub>3</sub>O<sub>4</sub> *J. Phys. Soc. Jpn* **53** 312-7
- [2] Zhang Z and Satpathy S 1991 Electron states, magnetism, and the Verwey transition in magnetite *Phys. Rev. B* **44** 13319-31
- [3] Bataille A M, Moussy J B, Paumier F, Gota S, Guittet M J, Gautier-Soyer M, Warin P, Bayle-Guillemaud P, Seneor P, Bouzehouane K and Petroff F 2005 Crystalline gamma-Al<sub>2</sub>O<sub>3</sub> barrier for magnetite-based magnetic tunnel junctions *Appl. Phys. Lett.* **86** 012509-3
- [4] Kado T, Saito H and Ando K 2007 Room-temperature magnetoresistance in magnetic tunnel junctions with Fe<sub>3</sub>O<sub>4</sub> electrode *J. Appl Phys.* **101** 09J511-3
- [5] Alexe M, Ziese M, Hesse D, Esquinazi P, Yamauchi K, Fukushima T, Picozzi S and Gösele U 2009 Ferroelectric Switching in Multiferroic Magnetite (Fe<sub>3</sub>O<sub>4</sub>) Thin Films *Adv. Mater.* **21** 4452-5
- [6] Hu G and Suzuki Y 2002 Negative Spin Polarization of Fe<sub>3</sub>O<sub>4</sub> in Magnetite/Manganite-Based Junctions *Phys. Rev. Lett.* **89** 276601
- [7] Margulies D T, Parker F T, Rudee M L, Spada F E, Chapman J N, Aitchison P R and Berkowitz A E 1997 Origin of the Anomalous Magnetic Behavior in Single Crystal Fe<sub>3</sub>O<sub>4</sub> Films *Phys. Rev. Lett.* **79** 5162-5
- [8] Celotto S, Eerenstein W and Hibma T 2003 Characterization of anti-phase boundaries in epitaxial magnetite films *Eur. Phys. J. B* **36** 271-9
- [9] Ziese M and Blythe H J 2000 Magnetoresistance of magnetite *J. Phys.: Cond. Matt.* **12** 13
- [10] Koch C T 2002 Determination of Core Structure Periodicity and Point Defect Density along dislocations, *PhD Thesis*, Arizona State University
- [11] Kosuke M, Vlado K L, Leonardo L, Hideo H and Tomofumi S 2013 Fe<sub>3</sub>O<sub>4</sub>(111) thin films with bulk-like properties: growth and atomic characterization *J. Phys. D: Appl. Phys.* **46** 022001
- [12] Lari L, Lea S, Feeser C, Wessels B W and Lazarov V K 2012 Ferromagnetic InMnSb multi-phase films study by aberration-corrected (scanning) transmission electron microscopy *J. Appl. Phys.* **111** 07C311-3